

**ISSN 2518-1491 (Online),  
ISSN 2224-5286 (Print)**

ҚАЗАҚСТАН РЕСПУБЛИКАСЫ  
ҰЛТТЫҚ ҒЫЛЫМ АКАДЕМИЯСЫНЫҢ

Д.В. Сокольский атындағы «Жанармай,  
катализ және электрохимия институты» АҚ

# **Х А Б А Р Л А Р Ы**

## **ИЗВЕСТИЯ**

НАЦИОНАЛЬНОЙ АКАДЕМИИ НАУК  
РЕСПУБЛИКИ КАЗАХСТАН  
АО «Институт топлива, катализа и  
электрохимии им. Д.В. Сокольского»

## **NEWS**

OF THE ACADEMY OF SCIENCES  
OF THE REPUBLIC OF KAZAKHSTAN  
JSC «D.V. Sokolsky institute of fuel, catalysis  
and electrochemistry»

**SERIES  
CHEMISTRY AND TECHNOLOGY**

**4 (442)**

**JULY – AUGUST 2020**

PUBLISHED SINCE JANUARY 1947

PUBLISHED 6 TIMES A YEAR

ALMATY, NAS RK

---

---

NAS RK is pleased to announce that News of NAS RK. Series of chemistry and technologies scientific journal has been accepted for indexing in the Emerging Sources Citation Index, a new edition of Web of Science. Content in this index is under consideration by Clarivate Analytics to be accepted in the Science Citation Index Expanded, the Social Sciences Citation Index, and the Arts & Humanities Citation Index. The quality and depth of content Web of Science offers to researchers, authors, publishers, and institutions sets it apart from other research databases. The inclusion of News of NAS RK. Series of chemistry and technologies in the Emerging Sources Citation Index demonstrates our dedication to providing the most relevant and influential content of chemical sciences to our community.

Қазақстан Республикасы Ұлттық ғылым академиясы "ҚР ҰҒА Хабарлары. Химия және технология сериясы" ғылыми журналының Web of Science-тің жаңаланған нұсқасы Emerging Sources Citation Index-те индекстелуге қабылданғанын хабарлайды. Бұл индекстелу барысында Clarivate Analytics компаниясы журналды одан әрі the Science Citation Index Expanded, the Social Sciences Citation Index және the Arts & Humanities Citation Index-ке қабылдау мәселесін қарастыруды. Web of Science зерттеушілер, авторлар, баспашилар мен мекемелерге контент тереңдігі мен сапасын ұсынады. ҚР ҰҒА Хабарлары. Химия және технология сериясы Emerging Sources Citation Index-ке енүі біздің қоғамдастық үшін ең өзекті және беделді химиялық ғылымдар бойынша контентке адалдығымызды білдіреді.

НАН РК сообщает, что научный журнал «Известия НАН РК. Серия химии и технологий» был принят для индексирования в Emerging Sources Citation Index, обновленной версии Web of Science. Содержание в этом индексировании находится в стадии рассмотрения компанией Clarivate Analytics для дальнейшего принятия журнала в the Science Citation Index Expanded, the Social Sciences Citation Index и the Arts & Humanities Citation Index. Web of Science предлагает качество и глубину контента для исследователей, авторов, издателей и учреждений. Включение Известия НАН РК в Emerging Sources Citation Index демонстрирует нашу приверженность к наиболее актуальному и влиятельному контенту по химическим наукам для нашего сообщества.

Бас редакторы  
х.ғ.д., проф., КР ҮҒА академигі  
**М.Ж. Жұрынов**

Редакция алқасы:

**Агабеков В.Е.** проф., академик (Белорус)  
**Баешов А.Б.** проф., академик (Қазақстан)  
**Бұркітбаев М.М.** проф., академик (Қазақстан)  
**Волков С.В.** проф., академик (Украина)  
**Воротынцев М.А.** проф., академик (Ресей)  
**Газалиев А.М.** проф., академик (Қазақстан)  
**Джусипбеков У.Ж.** проф., корр.-мүшесі (Қазақстан)  
**Жармағамбетова А.К.** проф. (Казакстан), бас ред. орынбасары  
**Жоробекова Ш.Ж.** проф., академик (Қырғыстан)  
**Иткулова Ш.С.** проф. (Қазақстан)  
**Манташян А.А.** проф., академик (Армения)  
**Пралиев К.Д.** проф., академик (Қазақстан)  
**Рахимов К.Д.** проф., академик (Қазақстан)  
**Рудик В.** проф., академик (Молдова)  
**Стрельцов Е.** проф. (Белорус)  
**Тельтаев Б.Б.** проф., академик (Қазақстан)  
**Тодераш И.** проф., академик (Молдова)  
**Тулеуов Б.И.** проф., академик (Қазақстан)  
**Фазылов С.Д.** проф., академик (Қазақстан)  
**Фарзалиев В.** проф., академик (Әзіrbайжан)  
**Халиков Д.Х.** проф., академик (Тәжікстан)  
**Шайхутдинов Е.М.** проф., академик (Қазақстан)

«КР ҮҒА Хабарлары. Химия және технология сериясы».

ISSN 2518-1491 (Online),

ISSN 2224-5286 (Print)

Меншіктенуші: «Қазақстан Республикасының Үлттық ғылым академиясы» Республикалық қоғамдық бірлестігі (Алматы қ.).

Қазақстан Республикасының Ақпарат және қоғамдық даму министрлігінің Ақпарат комитетінде 29.07.2020 ж. берілген № KZ66VPY00025419 мерзімдік басылым тіркеуіне қойылу туралы күелік.

Мерзімділігі: жылдан 6 рет.

Тиражы: 300 дана.

Редакцияның мекенжайы: 050010, Алматы қ., Шевченко көш., 28; 219, 220 бөл.; тел.: 272-13-19; 272-13-18,  
<http://chemistry-technology.kz/index.php/en/arhiv>

© Қазақстан Республикасының Үлттық ғылым академиясы, 2020

Редакцияның мекенжайы: 050100, Алматы қ., Қонаев к-сі, 142, «Д. В. Сокольский атындағы отын, катализ және электрохимия институты» АҚ, каб. 310, тел. 291-62-80, факс 291-57-22, e-mail:orgcat@nursat.kz

Типографияның мекенжайы: «NurNaz GRACE», Алматы қ., Рысқұлов көш., 103.

Г л а в н ы й р е д а к т о р  
д.х.н., проф., академик НАН РК  
**М.Ж. Журинов**

Р е д а к ц и о н на я кол л е г и я:

**Агабеков В.Е.** проф., академик (Беларусь)  
**Баешов А.Б.** проф., академик (Казахстан)  
**Буркитбаев М.М.** проф., академик (Казахстан)  
**Волков С.В.** проф., академик (Украина)  
**Воротынцев М.А.** проф., академик (Россия)  
**Газалиев А.М.** проф., академик (Казахстан)  
**Джусипбеков У.Ж.** проф., чл.-корр. (Казахстан)  
**Жармагамбетова А.К.** проф. (Казахстан), зам. гл. ред.  
**Жоробекова Ш.Ж.** проф., академик (Кыргызстан)  
**Итқұлова Ш.С.** проф. (Казахстан)  
**Манташян А.А.** проф., академик (Армения)  
**Пралиев К.Д.** проф., академик (Казахстан)  
**Рахимов К.Д.** проф., академик (Казахстан)  
**Рудик В.** проф., академик (Молдова)  
**Стрельцов Е.** проф. (Беларусь)  
**Тельтаев Б.Б.** проф., академик (Казахстан)  
**Тодераш И.** проф., академик (Молдова)  
**Тулеуов Б.И.** проф., академик (Казахстан)  
**Фазылов С.Д.** проф., академик (Казахстан)  
**Фарзалиев В.** проф., академик (Азербайджан)  
**Халиков Д.Х.** проф., академик (Таджикистан)  
**Шайхутдинов Е.М.** проф., академик (Казахстан)

«Известия НАН РК. Серия химии и технологий».

ISSN 2518-1491 (Online),

ISSN 2224-5286 (Print)

Собственник: Республиканское общественное объединение «Национальная академия наук Республики Казахстан» (г. Алматы).

Свидетельство о постановке на учет периодического печатного издания в Комитете информации Министерства информации и общественного развития Республики Казахстан № KZ66VPY00025419, выданное 29.07.2020 г.

Периодичность: 6 раз в год.

Тираж: 300 экземпляров.

Адрес редакции: 050010, г. Алматы, ул. Шевченко, 28; ком. 219, 220; тел. 272-13-19; 272-13-18,  
<http://chemistry-technology.kz/index.php/en/arhiv>

© Национальная академия наук Республики Казахстан, 2020

---

Адрес редакции: 050100, г. Алматы, ул. Кунаева, 142, АО «Институт топлива, катализа и электрохимии им. Д.В. Сокольского», каб. 310, тел. 291-62-80, факс 291-57-22, e-mail:orgcat@nursat.kz

Адрес типографии: «NurNaz GRACE», г. Алматы, ул. Рыскулова, 103.

**Editor in chief**  
doctor of chemistry, professor, academician of NAS RK  
**M.Zh. Zhurinov**

**Editorial board:**

**Agabekov V.Ye.** prof., academician (Belarus)  
**Bayeshov A.B.** prof., academician (Kazakhstan)  
**Burkitbayev M.M.** prof., academician (Kazakhstan)  
**Volkov S.V.** prof., academician (Ukraine)  
**Vorotyntsev M.A.** prof., academician (Russia)  
**Gazaliyev A.M.** prof., academician (Kazakhstan)  
**Dzhusipbekov U.Zh.** prof., corr. member (Kazakhstan)  
**Zharmagambetova A.K.** prof. (Kazakhstan), deputy editor in chief  
**Zhorobekova Sh.Zh.** prof., academician (Kyrgyzstan)  
**Itkulova Sh.S.** prof. (Kazakhstan)  
**Mantashyan A.A.** prof., academician (Armenia)  
**Praliyev K.D.** prof., academician (Kazakhstan)  
**Rakhimov K.D.** prof., academician (Kazakhstan)  
**Rudik V.** prof., academician (Moldova)  
**Streltsov Ye.** prof. (Belarus)  
**Teltaev B.B.** prof., akademik (Kazakhstan)  
**Toderash I.** prof., academician (Moldova)  
**Tuleuov B.I.** prof., akademik (Kazakhstan)  
**Fazylov S.D.** prof., akademik (Kazakhstan)  
**Farzaliyev V.** prof., academician (Azerbaijan)  
**Khalikov D.Kh.** prof., academician (Tadzhikistan)  
**Shaihutdinov E.M.** prof., akademik (Kazakhstan)

**News of the National Academy of Sciences of the Republic of Kazakhstan. Series of chemistry and technology.**

**ISSN 2518-1491 (Online),**

**ISSN 2224-5286 (Print)**

Owner: RPA "National Academy of Sciences of the Republic of Kazakhstan" (Almaty).

The certificate of registration of a periodical printed publication in the Committee of information of the Ministry of Information and Social Development of the Republic of Kazakhstan **No. KZ66VPY00025419**, issued 29.07.2020.

Periodicity: 6 times a year.

Circulation: 300 copies.

Editorial address: 28, Shevchenko str., of. 219, 220, Almaty, 050010, tel. 272-13-19; 272-13-18,  
<http://chemistry-technology.kz/index.php/en/arhiv>

© National Academy of Sciences of the Republic of Kazakhstan, 2020

---

Editorial address: JSC «D.V. Sokolsky institute of fuel, catalysis and electrochemistry», 142, Kunayev str., of. 310, Almaty, 050100, tel. 291-62-80, fax 291-57-22, e-mail: orgcat@nursat.kz

Address of printing house: «NurNaz GRACE», 103, Ryskulov str, Almaty.

---

OF THE NATIONAL ACADEMY OF SCIENCES OF THE REPUBLIC OF KAZAKHSTAN  
**SERIES CHEMISTRY AND TECHNOLOGY**

ISSN 2224-5286

<https://doi.org/10.32014/2020.2518-1491.69>

Volume 4, Number 442 (2020), 89 – 95

UDC 691.175.5.8

IRSTI 31.25.15

**A.N. Nurlybayeva, E.I. Rustem, A.A. Sholak, G.A. Seitbekova,  
M.S. Kalmakhanova, C.C. Akbolatova, A.A. Edilbaeva, D.A. Kulbaeva**

Taraz University named after M.Kh. Dulati

## **DETERMINATION OF THE GLASS TRANSITION TEMPERATURE OF METHACRYLATE COPOLYMERS**

**Abstract.** We have obtained a new synthetic copolymers based on methyl methacrylate (MMA) and butyl methacrylate (BMA), with use of the dinitrile as an initiator of Azobisisobutyronitrile acid (AIBN). Hence, the obtained results show the important role of the structure of the polymer melt at a specific temperature or heat resistance intensive degradation of polymeric materials and other characteristics of the TGA. Heat resistance, as well as a certain temperature loss of the samples depends on the chemical structure of polymers, expressed in terms of the glass transition temperature, the compactness of the macromolecular coil in the copolymer, which is also determined by the structure of the coil. The role of the latter in determining the thermal resistance decreases as the glass transition temperature of the copolymer. It was found that the thermal degradation of butyl methacrylate copolymers studied by the mechanism of copolymerization and decomposition side butyl substituent.

**Keywords:** methyl methacrylate, butyl methacrylate, copolymers, differential scanning calorimetry (DSC), thermo gravimetric analysis (TGA).

**Introduction.** Self-curing PMMA are materials formulated by the mixing of two-component, one solid (powder) based on PMMA spherical beads and another liquid includes monomer and an initiator to enable the polymerization reaction to occur at room temperature and a high level of heat being generated during the exothermic reaction. In self-curing, the polymerization reaction of methacrylate monomers is initiated by the activation reaction of BPO, with an amine accelerator at room temperature, which gives free radicals for addition to monomer molecules [3]. A high level of heat being generated during the exothermic reaction [1]. Authors [2] prepared copolymer latexes based on methyl methacrylate (MMA) and butyl methacrylate (BMA) using macroradical initiator technique. Different ratios of acrylic monomers were designed to investigate the effect of monomer compositions on physico-mechanical properties of acrylic films for paint application. The results showed that, physico-mechanical properties increased with increasing the ratio of MMA in the copolymer. The work was further extended to include the application of the obtained copolymer latexes to make acrylic syrups containing varying content of MMA-monomer to be self curing and modify physico-mechanical properties of paint solvent free.

**Materials and apparatus.** Methyl methacrylate, butyl methacrylate, Azobisisobutyronitrile acid production company «Aldrich Chemical Co.» USA was used without further purification and other chemicals as ethanol and acetone used in this experiment.

**Synthesis and Characterization of Copolymer.** The preparation of copolymer and the methods of analysis (FT-IR and SEM) have been previously described [3]. DSC was carried out using a Perkin Elmer Differential Scanning Calorimeter DSC. The samples were tested under N<sub>2</sub> atmosphere at a scanning rate  $\pm 20^{\circ}\text{C min}^{-1}$ . The thermal gravimetric analysis (TGA) was conducted on a TGA/SDTA 851e under nitrogen flow.

**Structure of Copolymers.** The structure of the copolymer latexes based on methyl methacrylate (MMA) and butyl methacrylate (BMA) is shown in figure 1.

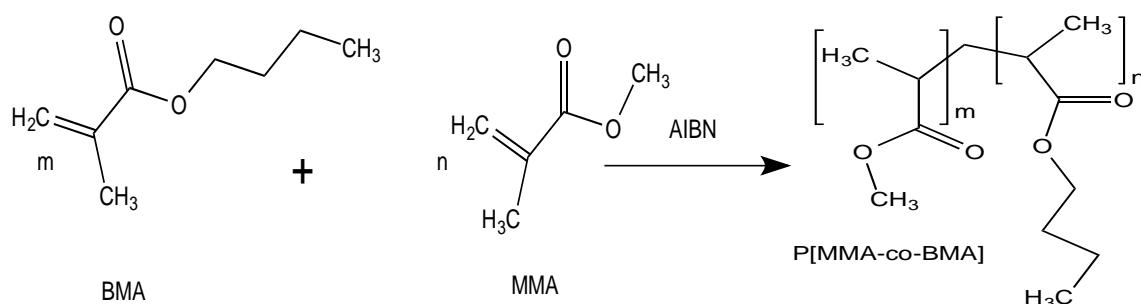


Figure 1 - General reaction for the synthesis of MMA/BMA copolymer [3]

The copolymer latexes were synthesized with different ratios (M1=10/90, M2=50/50 and M3=90/10 respectively) using azobisisobutyronitrile (AIBN) as free radical initiator. The properties of the prepared copolymer latexes have been previously reported by authors [3]. The results showed that physico-mechanical properties of the copolymer were increased by increasing the ratio of MMA in the copolymer latexes.

**Differential scanning calorimetry (DSC).** This assumption confirmed by the results of differential scanning calorimetry. DSC curves obtained are shown in figure 1 and in table 1.

Table 1 - Differential Scanning Calorimetry copolymer of MMA:BMA

[MMA-BMA] mol. %	T <sub>III</sub> , °C (a)	T <sub>III</sub> , °C (б)	Temperature range, °C (c)	Lost mass % (c)	Residual mass % (c)	PDTmax, °C (c)
10-90	43.30	34.15	25-280 280-500	1,7 98,3	98,3 0	435
50-50	63.10	57.12	24-277 277-500	1,4 93,5	93,5 0	426
90-10	98.40	94.34	25-274 274-500	10 90	90 0	420

Note – a – Values from DSC Analysis  
 б – Values determined by the Fox equation  
 с – Values derived from thermogravimetric analysis

Figure 2 shows a differential scanning calorimetry (DSC) of the studied samples. Seen from the curves that the samples undergo transformations, there is no monotony and regularity of change DSK - signal with increasing temperature. Therefore, we can assume that the melting copolymers requires energy, which is reflected by a sharp decrease in the DSC signal. From the DSC data it follows that the curve of the copolymer of MMA:BMA has an endothermic peak at 98°C, which corresponds to the glass transition temperature. Then, from 100 to 200°C in all systems, probably no chemical reaction occurs, and DSC - signal changes due to the removal of volatile impurities. The results obtained are in good agreement with the known views on the mechanism of thermal transformations of methacrylates [4], DSC and TGA data are in good agreement. Based on TGA and DSC data expansion process systems investigated under the temperature can be divided into three areas:

I - 10 to 250°C - an area resistant to aging;

II - from 325 to 425°C - region of rapid aging of the destruction of the copolymer;

III - above 450°C - the area of destruction.

Decomposition MMA:BMA is mainly on the mechanism of copolymerization, and accompanied by the destruction of lateral substituents of the methacrylate units in the copolymer can be expanded through the destruction of the lateral ester groups.

Destructive flow starts at 250°C. In which the endothermic peak at 325°C indicates the gap of methacrylate linkages and an exothermic peak area at 450°C – resulted by oxidation. Thus, copolymers based on MMA: BMA possess high thermal stability and are more resistant to thermal degradation.

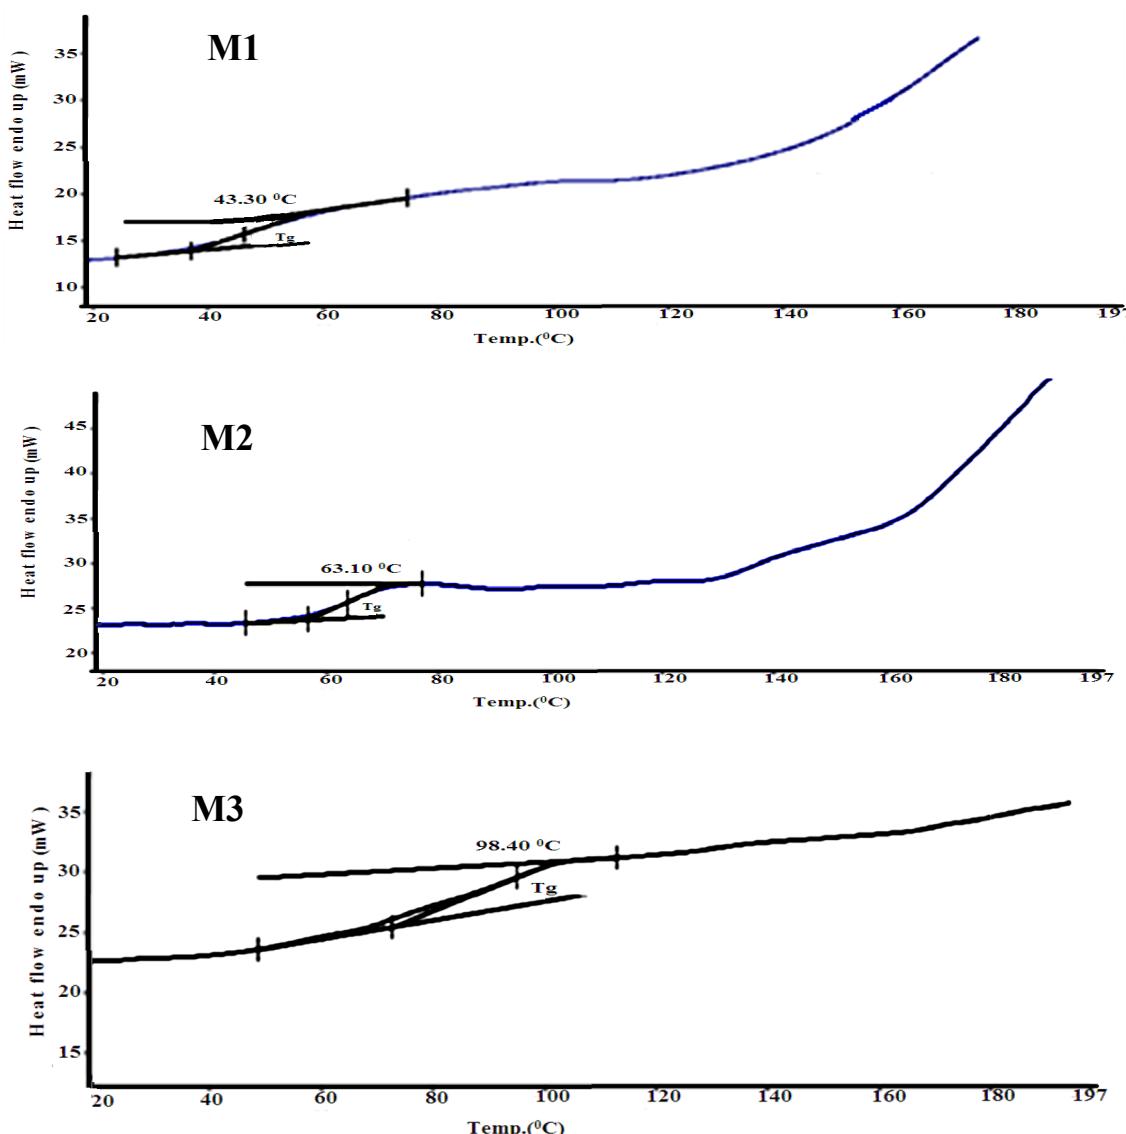


Figure 2 - DSC curves for polymers MMA: BMA 10:90 (1), 50:50 (2), 90:10 (3)

**Thermo gravimetric analysis (TGA).** To study the thermo physical properties of the synthesized copolymers and the starting reagents, studying these thermal properties by thermo gravimetric analysis (TGA) [8, 9]. TGA results are presented in table 1 and figure 3.

In a first step (20...280°C) going destruction of oxygen-containing groups: the carbonyl and ether, which is accompanied by mass loss of the sample 12, 5...13, 6 %. (table 1). Intensive thermal destruction corresponds to the interval 280–400°C, the loss of mass is 67, 5...68, 4 %.

Figure 3 shows the TGA - curves copolymer MMA: BMA, weight loss of the copolymer observed at 250°C, this is due to the loss and removal of volatile impurities. A loss of mass 10% observed at 225°C. The rate of thermal-oxidative decomposition of the copolymer increases markedly with temperature 425°C. The endothermic effect at 325°C, in which 450°C becomes exothermic peak showing the thermal oxidative degradation of the polymer [5, 6]. Over 450°C mass is removed and the remaining 20% of solid residue (see figure 2). The total drop weight is 80%.

The glass transition temperature of copolymers obtained by radical copolymerization in the presence of a dinitrile, Azobisisobutyronitrile acid, is higher than for the homopolymers, which indicates the formation of block copolymers. To analyze the properties of the copolymers are selected in the two monomers, which were used in the copolymerization reactions of methyl methacrylate (MMA), butyl methacrylate (BMA).

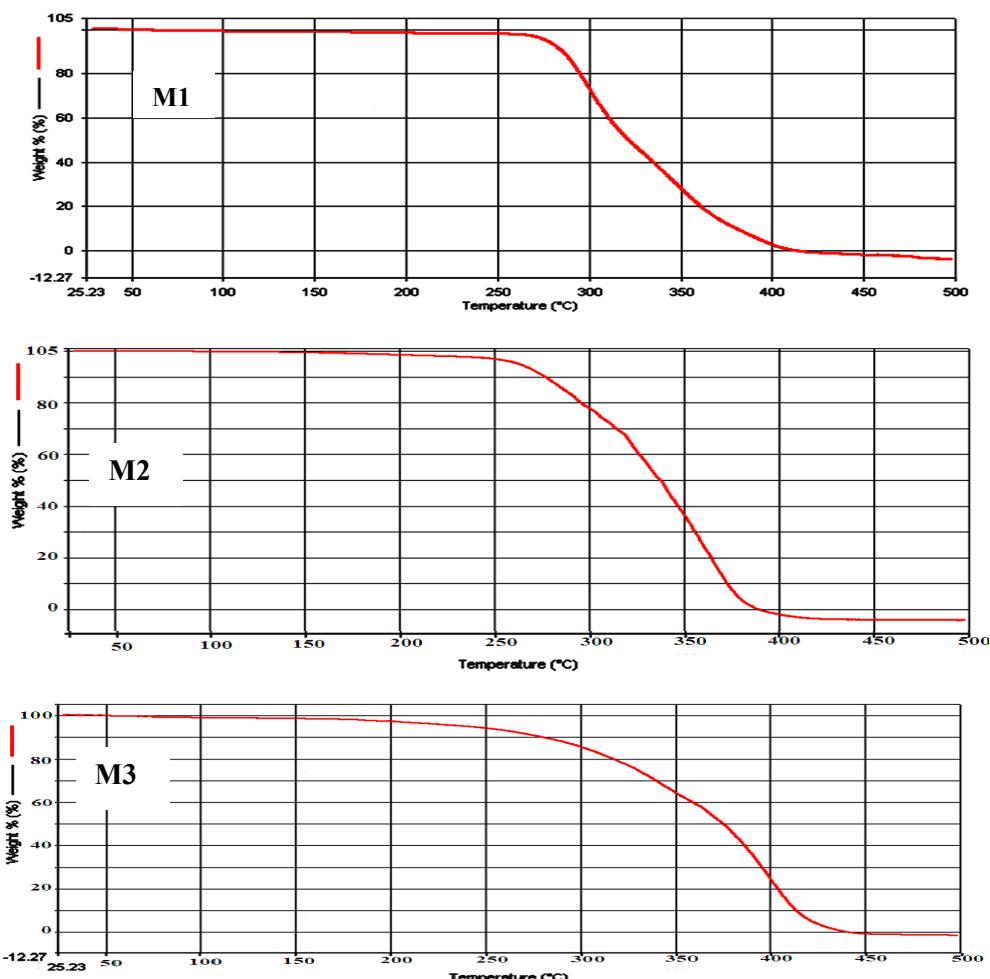


Figure 3 - The mass loss versus the temperature of copolymer.  
Composition MMA: BMA 10:90 (1), 50:50 (2), 90:10 (3)

Copolymers based on these compounds are completely amorphous high molecular weight substances which are easily formed in the block and suitable for thermal characteristics of study [7, 8].

The glass transition temperature of copolymers  $T_C$  calculated by the following equations.

$$\frac{1}{T_g} = \frac{W_1}{T_{g1}} + \frac{W_2}{T_{g2}} + \frac{W_3}{T_{g3}}$$

where  $T_C$  – The glass transition temperature of the copolymer,  $T_{g1}$  and  $T_{g2}$  – two glass transition temperatures of homopolymers and  $W_1$ , и  $W_2$  - weight of the two repeat units in the copolymer.

In general, there is good agreement between the calculated and experimental values of  $T_C$ . When using the experimental values of  $T_C$  for homo polymers and substituting them into the equation in most cases corresponds to the calculation experiment is somewhat improved. The calculated values of the characteristics defined for the ideal polymer system.

**Conclusion.** Polyampholytic properties of cross linked copolymers of MMA: BMA, partly due to the presence of unsaturated groups and carboxyl methacrylate structure characteristic for which presence confirmed also that by decreasing the content of the hydrophobic monomer MMA copolymers are obtained which are insoluble in water. Ionization of the carboxyl groups is a major contributor to the process of swelling and aspirations to the distribution of solvent throughout the volume of the polymer network.

MMA:BMA decomposition proceeds predominantly by the copolymerization mechanism, and is also accompanied by the destruction of side substituents; some of the methacrylic units in the copolymer decompose through the destruction of side ether groups.

**А.Н. Нурлыбаева, Е.И. Рустем, А.А. Шолақ, Г.А. Сейтбекова,  
М.С. Калмаханова, С.С. Ақболатова, А.А. Еділбаева, Д.А. Кулбаева**

М.Х. Дулати атындағы Тараз мемлекеттік университеті, Тараз, Қазақстан

## **МЕТАКРИЛАТ СОПОЛИМЕРЛЕРІНІҢ ШЫНЫЛАНУ ТЕМПЕРАТУРАСЫН АНЫҚТАУ**

**Аннотация.** Жұмыс мақсаты ретінде қанықпаган түрлі метакрил мономері негізінде жаңа сополимер синтезделіп алынды. Жаңа түрлі қатынастағы сополимерлер ММА-БМА синтезделді және физика-химиялық қасиеттері зерттелді.

Негізгі нәтижелер:

- алғаш рет ММА-БМА негізінде сополимерлер бастапқы коспадағы мономердің түрлі қатынастағы массада бос радикалды сополимерлену әдісі арқылы синтезделді;
- алынған сополимер ТГТ және ДСК әдісі негізінде термиялық қасиеттер қарастырылды. Осы мәліметтер негізінде шынылану температурасы анықталды.

Шынылану температурасы ( $T_g$ ) – полимерлердің маңызды параметрінің бірі, полимерлердің жылу сыйымдылық өлшемі ретінде кеңірек қолданылады. Бұл әдіс үлгілерді белгілі жылдамдықпен қыздыру барысында белінген жылу ағынын өлшеуге негізделген. Осы жылу ағыны дифференциалды сканерлеуші колориметрлік қондырығыда жазылады. Сополимердің шынылану температурасы осы мономерлер негізінде алынған жекелеген гомополимер  $T_g$  мәнінің арасында болады және сополимер құрамында белгілі бір мономер буынының мөлшері көп болуына байланысты мәні жылжып отырады. Полиметилметакрилаттың (ПММА) шынылану температурасы 105-120°C, ал полибутилметакрилаттың шынылану температурасы 20°C көрсетеді. Зерттелген ММА-БМА сополимерінің шынылану температурасы бастапқы мономер құрамындағы ММА мөлшері 90% (M3) болғанда 98°C, ал 50% (M2) көрсеткенде 63°C және 10% (M1) болғанда 43°C тең екені анықталды. Сополимер құрамында ММА мономерінің мөлшері көп болған сайын шынылану температурасы ПММА шынылану температурасына жакындей түсетіні байқалады. Фокс тендеуі арқылы анықталған мәні тәжірибелік мәнмен ұқсастығын аңғаруға болады.

Бұл термогравиметриялық талдау (ТГТ) – дифференциалды сканерлеуші колориметриялық талдау сияқты кеңінен қолданылатын әдіс болып саналады. Осы әдіспен үлгі массасының не массалық үлесінің температуралаға немесе уақытқа тәуелді өзгерісін өлшейді. Бұл талдау тұрақты атмосфералық қысымда және 25-5000°C температуралық диапазонында 1000 С / мин жылдамдықтағы газ тәріздес азотты қолдану арқылы жасалды. Жұмыста зерттелген сополимерлердің деструкцияға ұшырау жағдайы көрсетілген.

Полимердегі мономерлердің түрлі қатынасына байланысты шынылау температурасы ( $T_g$ ) үнемі өзгеріп отырады. Осы полимерлер қатылығын  $T_g$  шынылау температурасымен анықтайды, оған Фокстың эмпирикалық тендеуін қолдану арқылы төмендегідей есептеу жүргізілді.

Осындай термокатыланған полимерлер үшін есептелген шынылау температурасы ( $T_g$ ) үлдірдің соңғы  $T_g$  мәні емес, өйткені полимер тізбектері тігілген сайын оның  $T_g$  температурасы жоғарлайтынын ескеру қажет.

Синтезделген ММА-БМА сзыбықты сополимерінің термомеханикалық қасиеттері зерттелді және бастапқы реагенттің термиялық қасиеттерін ТГТ арқылы анықтау үшін мәліметтер қолданылды. ММА буыны 10% (M1) болғанда 25-280°C аралығында сополимер бастапқы салмағының 1,7% жоғалтса, ал ММА буыны 90% (M3) болғанда 25-274°C температура аралығында 10% массасын жоғалтады. Бастапқы сатыда үлгі құрамындағы дымқыл, су, еріткіш қоспаларының температурасын жоғарылатқанда, олар жылдам ыдырайды. Ал 280-500°C температуралық аумакта екінші рет массасын жоғалтады. Алғашкы үлгілер жалпы массасының 98% массасынан айырылса, соңғы үлгі жалпы массасының 90% жоғалтады. Сополимердің максималды ыдырау температурасы да (PDT) 435°C, 426°C, 420°C температуралық көрсетіп, ММА буыны 10%-дан 90%-ға артқан сайын төмендейтінін аңғаруға болады. Максималдық ыдырау температурасы полимер құрылымына байланысты. Алынған нәтижелер жұмыста келтірілген метакрилаттың өзгерісінің жылу механизмдеріне сәйкес келеді.

Алынған мәліметтер негізінде ТГТ және ДСК бойынша ыдырау үдерісіндегі зерттелген жүйеге температура есери 3 аймаққа келесідей беліннетіні анықталды.

I – 10-нан 250°C дейін – тозуға кедергі аймағы; II – 325-тен 425°C дейін – сополимер деструкциясының тез тозу аймағы; III – 450°C жоғары – деструкция аймағы.

**Түйін сөздер:** метилметакрилат, бутилметакрилат, сополимерлер, дифференциалды сканерлеу калориметриясы (ДСК), термогравиметриялық талдау (ТГА).

А.Н. Нурлыбаева, Е.И. Рустем, А.А. Шолақ, Г.А. Сейтбекова,  
М.С. Калмаханова, С.С. Ақболатова, А.А. Еділбаева, Да.А. Кулбаева

Таразский университет им. М.Х. Дулати

## ОПРЕДЕЛЕНИЕ ТЕМПЕРАТУРЫ СТЕКЛОВАНИЯ МЕТАКРИЛАТНЫХ СОПОЛИМЕРОВ

**Аннотация.** Для этой цели был синтезирован новый сополимер на основе различных ненасыщенных метакриловых мономеров. Синтезированы новые сополимеры разных соотношений MMA-БМА и изучены их физико-химические свойства.

Основные результаты:

- Впервые на основе MMA-БМА сополимеры были синтезированы методом свободно радикальной сополимеризации мономера в исходной смеси в разных массах.

- Термические свойства полученного сополимера были изучены методом ТГТ и ДСК. На основании этих данных была определена температура стеклования.

Температура стеклования ( $T_c$ ) является одним из важнейших параметров полимеров, которые широко используются в качестве критерия теплоемкости полимеров. Этот метод основан на измерении тепловых потоков, выделяемых при нагревании образцов с определенной скоростью. Этот тепловой поток регистрируется на дифференциальном сканере колориметра. Температура глазирования сополимера находится между значениями индивидуального гомополимера  $T_{sh}$ , полученного на основе этих мономеров, и эта величина варьируется из-за большого количества конкретных мономерных звеньев в сополимере.

Было обнаружено, что температуры стеклования исследуемого сополимера MMA-БМА составляют  $98^{\circ}\text{C}$  при 90% (M3),  $63^{\circ}\text{C}$  при 50% (M2) и  $43^{\circ}\text{C}$  при 10% (M1). Замечено, что чем выше содержание мономера MMA в сополимере, тем ближе температура стеклования к ПММА. Видно, что значения, определяемые уравнением Фокса, аналогичны экспериментальным значениям.

Этот термогравиметрический анализ (ТГТ) является широко используемым методом, таким как дифференциальный сканирующий колориметрический анализ. Этот метод измеряет изменение массы или массовой доли образца в зависимости от температуры или времени. Этот анализ был выполнен с использованием газообразного азота при постоянном атмосферном давлении и температурном интервале  $25\text{-}500^{\circ}\text{C}$  со скоростью  $100^{\circ}\text{C}/\text{мин}$ . Работа показывает, что изученные сополимеры разрушены.

Температура стеклования ( $T_c$ ) постоянно меняется из-за различных соотношений мономеров в полимере. Твердость этих полимеров определяется температурой стеклования  $T_c$ , до которой были выполнены следующие расчеты с использованием эмпирического уравнения Фокса.

Рассчитанная температура стеклования ( $T_c$ ) для таких термических полимеров не является конечной величиной  $T_c$  пленки, так как следует учитывать, что при сшивании полимерных цепей ее температура  $T_c$  увеличивается.

Термомеханические свойства синтезированного линейного сополимера MMA-БМА были изучены и данные были использованы для определения термических свойств исходного реагента с использованием ТГТ. Сополимер теряет 1,7% своей начальной массы в интервале  $25\text{-}2800^{\circ}\text{C}$  в парах MMA при 10% (M1) и теряет 10% своей массы в интервале температур  $25\text{-}2740^{\circ}\text{C}$  в парах MMA при 90% (M3). На начальной стадии, когда содержание влаги в образце, температура смесей воды и растворителя повышаются, они быстро разлагаются. А в температурном интервале  $280\text{-}500^{\circ}\text{C}$  теряет вес во второй раз. В то время как первые образцы теряют 98% от общей массы, последние образцы теряют 90% от общей массы. Можно видеть, что максимальная температура разложения сополимера (PDT) также уменьшается с увеличением температуры от 10% до 90%, что указывает на температуру  $435^{\circ}\text{C}$ ,  $426^{\circ}\text{C}$ ,  $420^{\circ}\text{C}$ . Максимальная температура разложения зависит от структуры полимера. Полученные результаты соответствуют тепловым механизмам изменения метакрилата, приведенным в работе.

На основании данных ТГА и ДСК процесс разложения исследуемых систем под действием температуры можно разделить на 3 области:

I – от  $10$  до  $250^{\circ}\text{C}$  – область, устойчивая к старению;

II – от  $325$  до  $425^{\circ}\text{C}$  – область быстрого старения с деструкцией сополимера;

III - выше  $450^{\circ}\text{C}$  – область деструкции.

Разложение MMA:БМА идет преимущественно по механизму сополимеризации, а также сопровождается разрушением боковых заместителей, часть метакриловых звеньев в сополимере разлагается через разрушение боковых эфирных групп.

**Ключевые слова:** метилметакрилат, бутилметакрилат, сополимеры, краска, пленка, прочность на растяжение, относительное удлинение при разрыве, твердость по Шору.

**Information about the authors:**

Nurlybayeva Aisha, PhD, associate Professor, Taraz University named after M.Kh. Dulati, rustem\_ergali@mail.ru, <https://orcid.org/0000-0001-9904-9979>;

Rustem Ergali, 2-year doctoral student Taraz University named after M.Kh. Dulati, rustem\_ergali@mail.ru, <https://orcid.org/0000-0001-8158-6290>;

Sholak Abdugali, candidate of technical sciences, Associate Professor, Taraz University named after M.Kh. Dulati, asholahov43@mail.ru, <https://orcid.org/0000-0003-1981-5034>;

Seitbekova Gulnazia, candidate of technical sciences, Professor, Taraz University named after M.Kh. Dulati, gul1970naz@mail.ru, <https://orcid.org/0000-0001-7087-7180>;

Kalmakhanova Marzhan, PhD, M.Kh.Dulati Taraz State University, marjanseitovna@mail.ru, <https://orcid.org/0000-0002-8635-463X>;

Akbolatova Symbat, master student 1 course, M.Kh.Dulati Taraz State University, akbolatova18@mail.ru, <https://orcid.org/0000-0002-6114-1283>;

Edilbaeva Aigul, master student 1 course, M.Kh.Dulati Taraz State University, aigul.edilbaeva@bk.ru <https://orcid.org/0000-0002-1998-2222>;

Kulbaeva Dilbar, master of Chemical Engineering, Senior Lecturer, dikush63@mail.ru, <https://orcid.org/0000-0001-7850-5453>

**REFERENCES**

- [1] Balke S.T., Hamielec A.E., Appl J. Polym. Sci., 17, 905-949, (1999).
- [2] Dunne N.J., Orr J.F. ITBM-RBM, 22, 2, 88–97, (2001).
- [3] Nurlybayeva A.N., Rustem E.I., Sadiyeva H.R., Seitbekova G.A., Darmenbayeva A.S., Kalmakhanova M.S., Egisinova A.M., Otinshieva U.T. Synthesis and application of acrylic films in paint and varnish materials// News of the National Academy of Sciences of the Republic of Kazakhstan. Series of chemistry and technology. 2020. Vol. 2(434), P. 44-49.
- [4] Ur'yash V.F., Izvozchikova V.A., Knyazeva N.Ye., Myasnikova I.B., Iosilevich I.N. // Int.Conf. Calorimetry, Experimental Thermodynamics, Thermal Analysis. Zakopane, 1997. P. 172
- [5] Zaikov GE Burning, degradation and stabilization of polymers. SPb.: Fundamentals and Technologies, 2008. 422 p.
- [6] Molodova AA, Volkova NV Emelyanov DN Sakhrova OI Laws of receipt and thermal aging acrylic copolymers // Bulletin of the University of Nizhny Novgorod. 2009. Vol. 3. P. 87-94.
- [7] Hohne G.W.H., Hemminger W.F., Flammersheim H.F., Differential scanning calorimetry. Berlin-Heidelberg: Springer-Verlag, 2003. 299 p.
- [8] Zislin SS, Senin NA, LM Terman, Semchikov YD Thermal decomposition of acrylic and methacrylic esters // Vysokomol. Comm. A. T. 1973. 14. №1. S. 238-249.

## **Publication Ethics and Publication Malpractice in the journals of the National Academy of Sciences of the Republic of Kazakhstan**

For information on Ethics in publishing and Ethical guidelines for journal publication see <http://www.elsevier.com/publishingethics> and <http://www.elsevier.com/journal-authors/ethics>.

Submission of an article to the National Academy of Sciences of the Republic of Kazakhstan implies that the described work has not been published previously (except in the form of an abstract or as part of a published lecture or academic thesis or as an electronic preprint, see <http://www.elsevier.com/postingpolicy>), that it is not under consideration for publication elsewhere, that its publication is approved by all authors and tacitly or explicitly by the responsible authorities where the work was carried out, and that, if accepted, it will not be published elsewhere in the same form, in English or in any other language, including electronically without the written consent of the copyright-holder. In particular, translations into English of papers already published in another language are not accepted.

No other forms of scientific misconduct are allowed, such as plagiarism, falsification, fraudulent data, incorrect interpretation of other works, incorrect citations, etc. The National Academy of Sciences of the Republic of Kazakhstan follows the Code of Conduct of the Committee on Publication Ethics (COPE), and follows the COPE Flowcharts for Resolving Cases of Suspected Misconduct ([http://publicationethics.org/files/u2/New\\_Code.pdf](http://publicationethics.org/files/u2/New_Code.pdf)). To verify originality, your article may be checked by the Cross Check originality detection service <http://www.elsevier.com/editors/plagdetect>.

The authors are obliged to participate in peer review process and be ready to provide corrections, clarifications, retractions and apologies when needed. All authors of a paper should have significantly contributed to the research.

The reviewers should provide objective judgments and should point out relevant published works which are not yet cited. Reviewed articles should be treated confidentially. The reviewers will be chosen in such a way that there is no conflict of interests with respect to the research, the authors and/or the research funders.

The editors have complete responsibility and authority to reject or accept a paper, and they will only accept a paper when reasonably certain. They will preserve anonymity of reviewers and promote publication of corrections, clarifications, retractions and apologies when needed. The acceptance of a paper automatically implies the copyright transfer to the National Academy of Sciences of the Republic of Kazakhstan.

The Editorial Board of the National Academy of Sciences of the Republic of Kazakhstan will monitor and safeguard publishing ethics.

Правила оформления статьи для публикации  
в журнале смотреть на сайте:

www:nauka-nanrk.kz

<http://chemistry-technology.kz/index.php/en/arhiv>

[ISSN 2518-1491 \(Online\), ISSN 2224-5286 \(Print\)](#)

Редакторы: *М. С. Ахметова, Д. С. Аленов, А. Ахметова*  
Верстка на компьютере *А.М. Кульгинбаевой*

Подписано в печать 06.09. 2020.  
Формат 60x881/8. Бумага офсетная. Печать – ризограф.  
9 пл. Тираж 300. Заказ 4.

*Национальная академия наук РК  
050010, Алматы, ул. Шевченко, 28, т. 272-13-18, 272-13-19*